

Collagel® Kit

The Collagel® Kit has all the components for creating 3D cell-seeded bioartificial type I collagen gels (see Table 1). For more information, see the Collagel® product webpage at

http://www.flexcellint.com/Collagel.htm.

Table 1. Collagel® Kit Materials per kit size


Tuble 1. Comagen	Ku muieriuis per ku size			
Component	Chemical	Volume (ml)		
		Mini	Midi	Maxi
Collagel [®]	Type I Collagen	8	16	32
	(3 mg/ml in 0.01 M HCl)			
Reagent A	5X MEM	2	4	8
Reagent B	Fetal Bovine Serum	1	2	4
Reagent C	1M Hepes	0.25	0.5	1
Reagent D	0.1 M NaOH in 5X MEM	0.5	1	2

Product Information Sheet 09/12/18 Rev. 2.0



PROTOCOL FOR PREPARATION OF 1 ML COLLAGEL® COLLAGEN GEL FOR GENERAL USE

- Reconstitute Reagent B (Fetal Bovine Serum, Lyophilized) in 1.2 mL of sterile water as instructed below.
- 2. In a 1.5 ml centrifuge tube, combine 160 μ l reagent A, 80 μ l reagent B, and 20 μ l reagent C.
- 3. In a second 1.5 ml centrifuge tube, combine 700 μl Collagel® and 40 μl reagent D. After mixing well, ensure that the pH of the Collagel®/Reagent D mixture is 7.0 7.2. If not, add 2.5 μl of Reagent D, mix well, and test again. Repeat until pH is in desired range.
- 4. Combine the two tubes and mix well by pipetting.
- 5. This gel solution may be used to resuspend your cell pellet or other constituents for plating. See Figure 2 for kinetics of gelation at 37 °C.

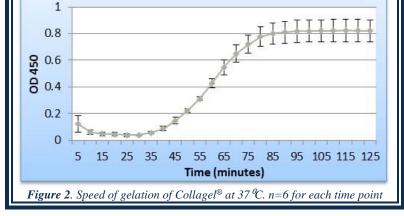

PROTOCOL FOR CASTING BIOARTIFICIAL CELL-POPULATED HYDROGELS (BAT) IN FLEXCELL® LINEAR TISSUE TRAIN® CULTURE PLATES

- 1. Prepare cells according to your established protocol for primary cultures or continuous cell lines in the medium of choice.
- 2. Release cells from their substrates with 0.05% trypsin, trypsin-EDTA, 0.05% bacterial collagenase, or other means
- 3. Add serum containing media to the cells to neutralize the trypsin or collagenase.
- 4. Count cells and determine the number of cells needed, approximately 50,000-200,000 cells in 150-200 μl Collagel® collagen gel for each well of a 6-well Tissue Train® culture plate. NOTE: Cell seeding density in a 3D gel will vary depending on cell type. We recommend testing cell seeding densities to determine the best cell number for your application and cell type.
- 5. Wash cells 2x with medium to remove trypsin or collagenase.
- 6. Position Tissue Train[®] plate with gasket on top of a Trough Loader[™] and ensure proper seating to achieve a sealed vacuum.
- 7. Initiate a maximum elongation (~90 kPa) static pull down regimen using the Flexcell® FX-5000™ Tension System. Note: For standard Collagel®, 2 hours of gelation time is recommended. It is also recommended that the vacuum be released slowly by 2% elongation of maximum every 6 seconds until 0% elongation is achieved.



8. Preparing the Collagel®-media matrix, see table below for example volumes. In a 1.5 ml tube (not supplied), combine reagents A, B and C. In a 5.0 ml tube (not supplied), add reagent D to the Collagel® and mix well (thoroughly mixed solution should become light peach in color). Remove 10 μl of the Reagent D-Collagel® mixture and apply to pH paper (not supplied) to ensure pH is neutral (7.0-7.2 is ideal). *Note: If not, add 2.5 μL Reagent D and check again. Repeat until pH is in desired range.* Add Reagent A, B, C mixture to the Collagel® mixture and mix well by pipetting. *Keep all reagents at 4°C or prepare on ice.*

Reagent	Volume (µl) (Example Ratios)	6-Well Tissue Train® (200 µl/BAT)	24-Well HTP Tissue Train® (50 μl/BAT)
A	160	288 μl	288 μΙ
В	80	144 μl	144 μl
C	20	36 μ1	36 μl
Collagel®	700	1260 μ1	1260 µl
D	40	72 μ1	72 µl
Total	1000	1800 μl	1800 μl

- 9. Resuspend the cell pellet in the complete Collagel®-media matrix and mix well by pipetting up and down.
- 10. Micropipette 200 µl cell constituted Collagel®-matrix into each linear trough of a Tissue Train® plate. First pipette a small drop of gel at each end of the trough, under the anchor stems. Then press the anchor stems into the trough and release several times, thoroughly wetting the tabs. Finally, fill the middle of the trough with gel, moving the pipette back and forth to create a uniform strip of gel in the well (see video of *Tissue Train® Bioartificial Tissue Fabrication with Uniaxial Strain* on Flexcell®'s web site, www.flexcellint.com).
- 11. Place baseplate into 37 °C 5% CO₂ incubator for 2 hours and allow the constructs to polymerize.
- 12. Near the end of the static pull down (approximately 10 minutes remaining) while the vacuum is still engaged, transfer baseplate to a tissue culture hood and add 3.0 ml complete growth media making sure to pipet very slowly to prevent undue motion to the gelling BATs.
- 13. Once vacuum has released, remove plates and place in incubator at appropriate growth conditions. Culture constructs according to the laboratories established protocol. It is recommended that the growth media be changed every 3 days.

PROTOCOL FOR PREPARATION OF FETAL BOVINE SERUM (REAGENT B)

- 1. Add 1.2 mL of sterile DI water to the lyophilized serum with a sterile 5 mL syringe and 22-gauge needle. Resuspend without foaming.
- 2. Draw the resuspended serum into the 1 mL syringe. Remove the 22-gauge needle and apply a $0.22~\mu M$ syringe filter to the 5 mL syringe. Express the reconstituted serum into a sterile 2 mL vial.
- 3. Store filtered solution at 4 °C. Use within one-two weeks of preparation. Alternatively, aliquot the reconstituted FBS in 100 μ L volumes and store at -20 °C until ready to use.
 - NOTE: User can also use FBS from their own source in place of the lyophilized FBS kit component Reagent B (Test source FBS to be sure the serum works in the kit before large scale use).

RECOMMENDED REAGENT STORAGE CONDITIONS

Reagent	Storage Temperature
Collagel®	4°C
Reagent A	4°C
Reagent B	4°C
Reagent C	4°C
Reagent D	4°C

ORDERING INFORMATION

Collagel® Kits are sold in 3 sizes: Mini (Cat. No. COLKIT-100A), Midi (Cat. No. COLKIT-100B), and Maxi (Cat. No. COLKIT-100C). A Mini kit has approximately enough solution to make BATs in eight 6-well linear Tissue Train® culture plates, a Midi kit has enough for sixteen 6-well plates, and a Maxi kit for thirty-two 6-well plates.

Flexcell® Collagel® is protected by the following patents: US Patents 8,663,988; 8,8577,500; 8,993,325; 9,018,009.